

# IR Thermography for the Nondestructive Evaluation of the Protective Coating Coverage on Steel Substrates

**Mohammed Omar and Kozo Saito**  
Dept. of Mechanical Engineering  
University of Kentucky  
Lexington KY 40506-0503

## ABSTRACT

The infrared thermography (thermal imaging) is considered a flexible, non-contact, and non-destructive tool used to evaluate wide variety of coating attributes (e.g. appearance and protective attributes). This paper addresses the application of thermographic systems in evaluating the protective-coating coverage over steel substrates in two different painting industries. First case is the inspection of the ballast ship tanks coating for "Holidays" or missed coated spots. The second describes the development of an automated thermographic system, designed to inspect for: thin coating, coat cracking, and coat chipping of an anti-corrosive paint applied on automotive steel containers.

This work describes the theory of detection and the thermographic system design and implementation that include the hardware and the software development, where an in-house code is used to process the acquired data.

## 1- Introduction

Coatings are applied on material surfaces to provide two main attributes. (1) Appearance that relates to the color dimensions and the geometrical aspect that features haze and gloss. (2) Protection, represented by its ability to protect against corrosion. This protection is achieved by utilizing a primer layer that functions through insulating the substrate from surrounding conditions (e.g. weathering effects). In the case of corrosion, this insulation protects by breaking the corrosion cycle (i.e. Anode, Cathode and an electrolyte) by shielding the steel substrate from the electrolyte (e.g. salt water). Because insulation is crucial, coverage and integrity of the coating must be accurately inspected to ensure it will protect as it is designed.

Infrared thermography or, IRT nondestructive applications constitute the thermal mapping of material surfaces to investigate its facial and/or its subsurface status that may affect its performance. This is done using photonic or bolometric arrays sensitive in the (1-13  $\mu m$ ) band of the electromagnetic spectrum [1]. IRT has been successfully used as a real-time thermal machine vision system for detecting thin paint spots on automotive fuel containers in [2]. Further, it has effectively been used to detect latent corrosion in different steel structures including bridges [3] and petroleum reservoirs [4]. Furthermore, Infrared thermography has also been used to measure the thickness of different types of coatings such as Thermal Barrier Coatings (TBC) applied to turbine blades [5, 6]. This technique has two advantages as an inspection method for coated structures: (1) no contact with the surface, enabling it to be applied in wet and dry settings, and (2) area coverage enabling it to be applied in large structures such as, ships' ballast tanks and bridges [7].

Next two sections of this manuscript introduces two case studies for the IRT coating inspection; one is the real-time, on-line detection of thin paint spots on coated steel fuel containers in automotive production lines. The second relates to IRT application in evaluating ships ballast tanks' coat coverage.

## 2- Fuel containers inspection


In this work, the targeted products are automotive steel fuel containers coated with a single layer of a waterborne, anti-corrosive protective coating (150-400  $\mu\text{m}$  in thickness). Those containers are mass-produced to serve as a safe fuel storage and supply source. For this case, the coating application problems to be detected were (1) thin paint (or spots missed, uncoated) and (2) chipping upon curing. Both kinds of defective application expose the substrate and thus may allow corrosion to begin if uncorrected.

The two current methods for inspecting these defectives are not optimal. Visual inspection by human operators is not continuous but relies on checks during certain time periods; industrial plant lighting conditions and the small size ( $\sim 0.4\text{ mm}$ ; see figure 1,a) of the defects make accurate inspection by the naked eye difficult. Visual inspection routines utilizing Charged Coupled Devices CCDs are also less than optimal for this application due to the rough surface profile (as shown in figure 2) and certain aspects of the surface geometry. Both of these factors cause light scattering that can mask defective spots.

The analytical study and the laboratory testing for this application are fully presented in [2], where a microbolometer infrared detector was used to scan the surface of the tank detecting the difference in thermal emission from the pinholes (behaving according to steel substrate thermal properties) and the well coated surroundings (emitting according to paint properties). This deviation is displayed in figure 2,b and quantitatively described later in the text.

Because, thermography requires thermal emission from the surface, the online deployment started with surveying the containers production cycle to decide where to install the system. Production lines for such containers use curing-ovens to cure and dry the coat film. Because these ovens operate at between 373–423 K, they can serve as a thermal stimulant, which eliminates the need for an external heating unit and consequently improves the system's reliability and compactness.

An industrial packaged thermal detector with  $320 \times 240$  array and 60Hz acquisition rate (commercial name A40M, FLIR MA,US) can be installed at the exit of the curing oven. This detector scans the container as it comes out of the oven, and interfaces the acquired thermograms through IEEE1394 link to processing unit. The on-site results are shown in figure 3. The processing logic is discussed in section 4.

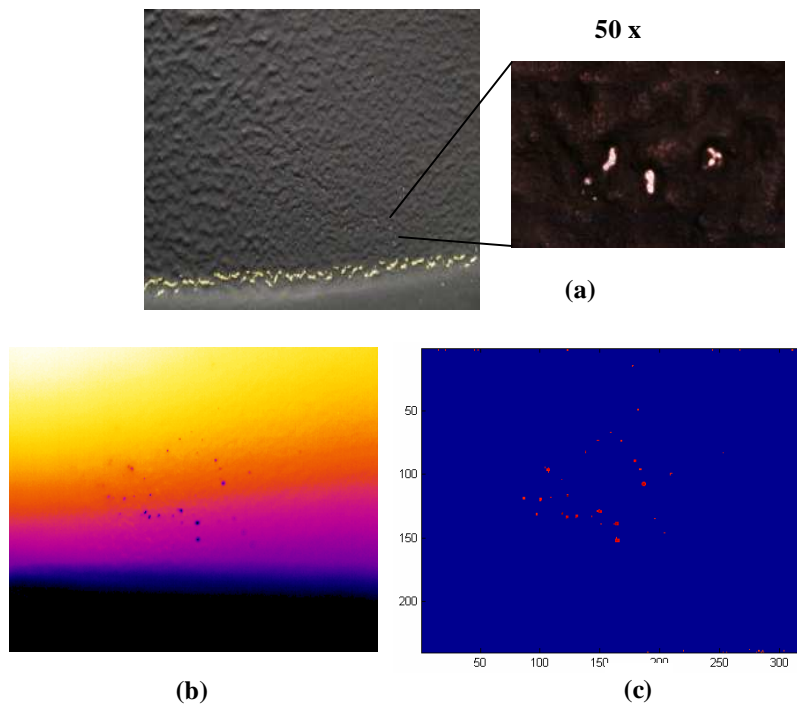

**Figure 1. Visual, thermal and post-processed images of an under coated sample container: (a) Visual image for thin spots, and under 50-x magnification. (b) Thermal image of the field view in a, and (c) Processed image**




**Figure 2. A color photograph showing surface profile of coated container**

### 3- Ballast tanks inspection

This section focuses on the evaluation of newly coated ships' ballast tanks with marine primers that range in thickness from 125 – 250 microns. Oil tankers and other medium to large size ships use the ballast tanks to stabilize its floating equipments, by filling it with seawater. Corroded ballast tanks not only affect their own performance but also the safety of the whole ship.. While, currently used tools are applied in an on-site (e.g. wet sponge) and/or an off-site modes (e.g. wave tank introduced by Marintek, Norway)[8], it still require: (1) a dry paint film, which delays the inspection and separate it from the application step, even though, what is desired is to merge the inspection and application in a single step "do it right the first time", to (a) save time and effort and (b) facilitate an immediate correction because, the cost of a touch job is about \$22/m<sup>2</sup>. (2) Physical contact, this requires accessibility to corners and cervices that are considered most critical for corrosion initiation, while those tanks complicated geometries and uniqueness challenge this accessibility. Those two shortcomings, in addition to the recently issued regulations [9] that enforce more stringent standards on the finished ballast tanks' and the increase in ships sizes, the tankers size went from 100,000 dwt to 500,000 dwt in 10 years [10], motivate the development of a nondestructive, non-contact and real time tool to evaluate the paint deposition quality in terms of coverage and layer thickness.

Visible techniques in the form of machine vision systems or human naked eye inspection offer a contact less operation, however still inadequate for the detection of coating pinholes due to (1) variability and availability of environments lighting, as in dark tanks and (2) its sensitivity to the inspected surfaces' profile and geometry, due to its dependence on reflection. Those two factors hinder the repeatability and the reliability of this test. In addition, visual inspection is a facial technique not capable of providing thickness information.

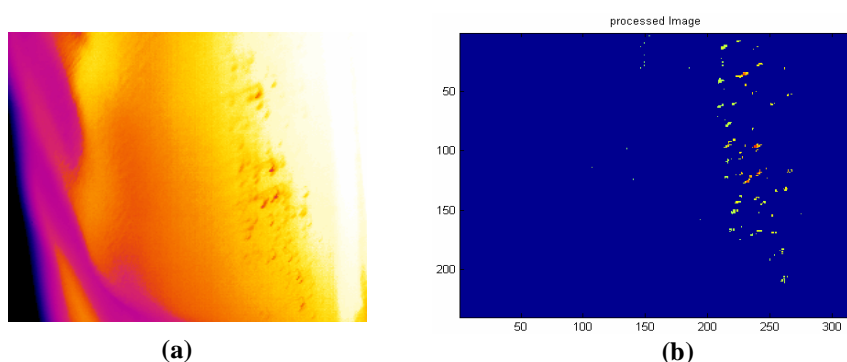



**Figure 3. An on-site test result: (a) Thin coating targets detected at the exit of curing oven, and (b) Corresponding processed thermogram.**

For the pinholes detection, we use a static mode of IRT through acquiring snap shot thermograms after heating the pinhole sample, this sample is shown in figure 4 and is prepared using drawdown blades on a 50 micron profile substrates. Two quartz-heating lamps with 400-watt intensity, installed along with the IR cam in a detection head figure 5, was used for 4 seconds, to heat the sample stimulating thermal emission. The pinholes behave according to

the substrate properties i.e.  $\kappa_{steel}, \rho_{steel}$  and  $Cp_{steel}$ , while the well coated surroundings have the thermal properties of the primer-coat. This creates the difference in the temperature reading across a missed coated region and another well-coated one, pictorially this is shown in figures 2,d and 8,c, and mathematically explained through the thermal mismatch factor or, the thermal reflection coefficient in equation (1), more details could be found in [11];

$$\Gamma = \frac{e_{coat} - e_{steel}}{e_{coat} + e_{steel}}, \quad (1)$$

where,  $e = \sqrt{\kappa \cdot \rho C_p}$  is the thermal inertia, the subscripts coat and steel refers to the use of the thermal properties (thermal conductivity  $\kappa$ , density  $\rho$  and specific  $C_p$ ) of the steel and the primer-coat respectively.

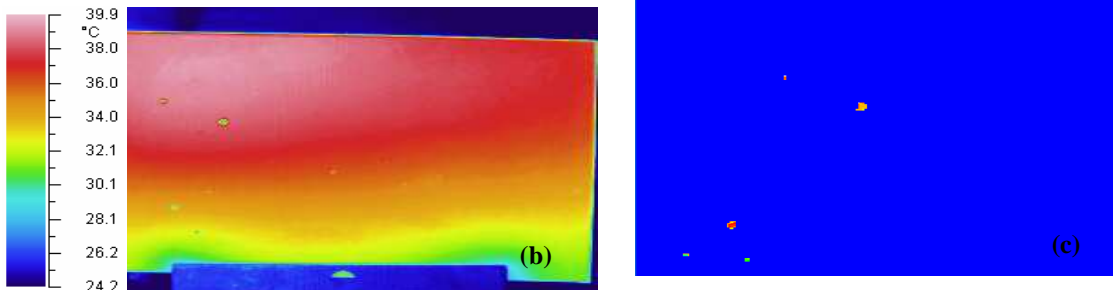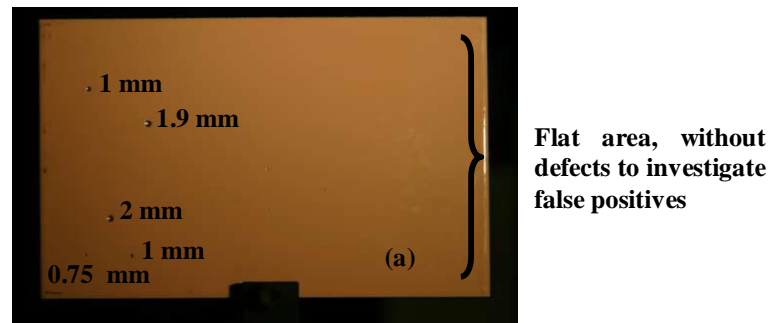


**Figure 4, (a) Photograph of the pinhole sample, (b) Thermal pinhole image (thermogram), color-bar indicates temperature readings and (c) Processed thermal image.**

#### 4. Data analysis

Traditional image analysis routines are not suitable for processing the acquired thermal images or thermograms, because of the heating non-uniformities, which could be a result of the high tolerances in protective coat-film thicknesses, the touch-up jobs and surface profile and geometry. All of this creates non-uniform thermal maps. To provide a complete automated detection package, image processing software is required to isolate the defectives from their surroundings. In [12] we introduced a new image processing routine based on dividing the thermogram into localized neighborhoods. The size of the local neighborhood should be selected such that it will be larger than the defect and sizes sought and assure a stable temperature across the region, but small enough to be contained within the smallest area of non-uniformity (its definition dependant on the application at hand). A relative thresholding step follows, where each pixel in the thermal image is compared against the average of its surrounding neighborhood; if it passes the criterion in (2), its value is boosted with multiples of the difference from the average otherwise its value is set to zero.

$$|T_{pix} - T_{avg.}| \geq \eta \cdot \sigma_{surr(i,j)} \quad (2)$$

Where  $T_{pix}$  is the temperature of central pixel,  $T_{avg.}$  is the kernel average temperature,  $\eta$  is a scaling factor dependant on the signal to noise ratio of the thermogram, and  $\sigma_{surr(i,j)}$  is the standard deviation of pixels in the local neighborhood surrounding  $(i, j)$ . To illustrate the effectiveness of this routine, we apply it to the thermogram shown in figure 1,b, 3,a and 4,b. The results, in figure 1,c, 3,b and 4,c show that the code successfully removed the non-uniform heating effects while detecting the thin spots.

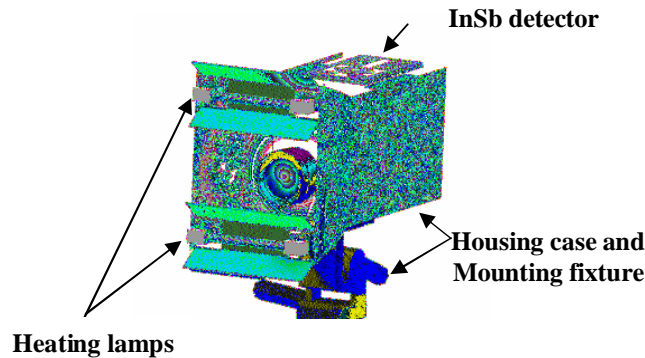

**Figure 5, The detection head used for pinhole detection**

To quantify the code performance, we utilize Tanimoto criterion (or, reveal ability  $Rev.$ ) described in equation (3), and first introduced in [13].

$$Rev. = \frac{N_{real} - N_{missed}}{N_{real} - N_{false}} \quad (3)$$

where,  $N$  is the number of defects and the subscripts *real*, *missed*, *false* refer to real defects, missed defects and false positives found in the processed image. Applying this criterion to the processed images results in average of  $Rev. = 95\%$ . One should bear in mind that applying Tanimoto's criterion for a single image with limited number of defectives is considered highly conservative, and so any  $Rev. > 80\%$  indicates effective processing.

#### 4. Conclusion

This paper presented the infrared thermography capability in the non-destructive evaluation of coated surfaces in terms of paint coverage; detecting pinholes. The fast and area coverage attributes of thermography, enabled the development of a real time thin paint detection system suitable for industrial production lines. This work also, presented the novel, successful application of thermography in detecting "Holidays" or pinholes in marine coatings through the development of a mobile, compact detection head. The in-house code, enables those two systems to be applied in an automated fashion that enables, (1) objective judgment, (2) record keeping, and (3) ease of standardization of the inspection criteria.

#### Acknowledgments

This study was sponsored in part by Toyota Motor Manufacturing.

### Reference:

1. X. Maldague "Theory and Practice of Infrared Technology for Nondestructive Testing", Wiley Interscience Publication 2001
2. M. Omar, K. Chuah, K. Saito, X. Liu and R. Alloo, "Thermal machine vision system for protective coat coverage inspection" Quantative Infrared Thermography QIRT Journal **2**, 2, 2005
3. G. Morel, A. Wyckhuse, X. Maldague, "Active Pulsed Infrared Thermography for Concrete Bridge Deck Inspection", J. CINDE **4**, 2001
4. T. Sakagami, S. Kubo "Applications of pulse heating thermography and lock-in thermography to quantitative nondestructive evaluations" Infrared Physics and Technology **43** 211-218, 2002
5. Bison P.G., Marinetti S., Grinzato E., Vavilov V., Cernuschi F. and Robba D., "Inspecting thermal barrier coatings by IR thermography" Thermosense XXV **5073**, 2003
6. Netzelmann U. and Walle G., "High speed thermography of thin metallic coatings" Photoacoustics and photothermal phenomenon 10th international conf. American inst. of Phys 1999
7. Lau S. K., Almond D. P. and Patel P. M., "Transient thermal wave techniques for the evaluation of surface coatings" Journal physics D: Applied Physics **24**, 1991
8. H. Void, "Evaluating protective coatings for ballast tanks", Protective Coatings Europe, **6** 18-22 1997
9. R. Malfanti, "Achieving cost effective specifications for ballast tank coatings", Protective Coatings Europe, **11** 32-38 1998
10. E. Askheim, O. Nakken, and B. Haugland, "How and Why Corrosion Protection of Ballast Tanks Has Become the Business of Classification How and Why Corrosion Protection of Ballast Tanks Has Become the Business of Classification Societies" Protective Coatings Europe, **6** 46-52, 1999
11. M. Omar, M.Hassan, K. Saito and R. Alloo, "IR thermography inspection of adhesion integrity" ASME Proceedings of IMECE **3**, Anaheim, CA 2004
12. M. Omar, M. Hassan, K. Saito and R. Alloo "IR self-referencing thermography for detection of in-depth defects" Journal of Infrared Physics and Technology, **46**, 4, 283-289, 2005
13. V. Yanisov, L. Yanisov, "The Reveal ability of defects in optical synthesis of thermograms from x-ray photographs of different aspects", Sov. J. NDT **12**, 1-9 1984

IR Thermography for the Nondestructive Evaluation of the Protective Coating Coverage on Steel Substrates. Article. Full-text available. Mohammed A Omar. Kozo Saito. The infrared thermography (thermal imaging) is considered a flexible, non-contact, and non-destructive tool used to evaluate wide variety of coating attributes (e.g. appearance and protective attributes). For the commonly encountered quantitative thermographic defect identification problem when the test piece is heated from one part of the outer boundary, our previous study showed that some parts of the defect boundary are sensitive to the initial defect boundary prediction of the conjugate gradient method. Active thermography is an advanced nondestructive testing procedure, which uses a thermography measurement of a tested material thermal response after its external excitation. This principle can be used also for non-contact infrared non-destructive testing (IRNDT) of materials. The IRNDT method is based on an excitation of a tested material by an external source, which brings some energy to the material. Halogen lamps, flash-lamps, ultrasonic horn or other sources can be used as the excitation source... Protective coatings non-destructive testing (PC/NDT) is a lifetime maintenance discipline that has been designed to provide a significant improvement in the maintainability of protective coatings. PC/NDT is based on the application of permanent foundation primer coats over-coated with expendable finish coats. Maintenance focuses on the repair or replacement of the finish coats, leaving the primer coats intact. Recoating is scheduled by black light-activated fluorescence (a type of non-destructive testing). It is critical that the bare-metal substrate be completely cleaned and conditioned to prevent under-film corrosion activity and provide a sound base for later maintenance recoat operations. IR thermography is one of the most attractive and successful techniques, which allows detecting the object's surface and subsurface defects remotely without harmful radiation effects of other technologies (such as X-ray imaging). In particular, Tahiliani et al. used a stainless steel mirror placed inside the pipe in order to view the reflected IR radiations using an IR camera [4]. Mancaruso et al. also took IR images by means of a 45° IR-mirror located in the elongated piston (in order to analyze fuels combustion in engines) [5]. However, all the aforementioned approaches do not allow carrying out on-field experiments in hard-to-reach places, for example, in curved internal pipes of heat exchangers or in spaces near gas turbine blades.